arXiv:cond-mat/0106408v1 [cond-mat.supr-con] 20 Jun 2001

Precise Tight-binding Description of the Band Structure of MgB_2

D. A. Papaconstantopoulos and M. J. Mehl
Center for Computational Materials Science, Naval Research Laboratory, Washington DC 20375-5000
(February 1, 2008)

We present a careful recasting of first-principles band structure calculations for MgB_2 in a non-orthogonal sp-tight-binding (TB) basis. Our TB results almost exactly reproduce our full potential linearized augmented plane wave results for the energy bands, the densities of states and the total energies. Our procedure generates transferable Slater-Koster parameters which should be useful for other studies of this important material.

The recent discovery of superconductivity in MgB_2[1] has created great interest in the study of this material, both to understand the mechanism of superconductivity and to explore other properties of MgB_2 and related materials. Intensive research has been carried out both by experimentalists[1–3] and theorists.[4–9] There have been several studies of the electronic structure of MgB_2 including total energy, band structure and phonon spectra calculations as well as evaluations of the electron-phonon coupling, which seems to have emerged as the prime candidate for explaining the superconducting behavior.

In this paper we present a highly accurate tight-binding (TB) description of the band structure and total energy of MgB_2. While there have been TB interpretations of the electronic structure of MgB_2 in the literature, a realistic recasting of the details of the first-principles electronic structure calculations is lacking. Our approach follows the NRL-TB methodology,[10,11] which is based on deriving a non-orthogonal TB Hamiltonian by fitting to both the total energy and energy band results of a first-principles full-potential Linearized Augmented Plane Wave (LAPW)[12,13] calculation using the Hedin-Lundqvist parametrization of the Local Density Approximation (LDA).[14] We first performed detailed LAPW calculations for MgB_2 in its ground state (AlB_2) structure, varying c and a, thus determining the LDA equilibrium volume. It was necessary to perform 17 independent LAPW calculations over a large range of volumes and c/a ratios. Our LAPW equilibrium parameters are c = 6.55 a.u. and a = 5.75 a.u., as compared to the experimental values of c = 6.66 a.u. and a = 5.83 a.u. As is usually the case the LDA underestimates the experimental values, here by about 1.5%.

All the above results, i.e., 17 values of the total energy and the energy bands for 76 k-points in the irreducible hexagonal Brillouin zone, were used as a database to determine the parameters of our tight-binding Hamiltonian. According to the NRL-TB scheme the on-site parameters depend on the density of the neighboring atoms and the hopping integrals have a polynomial dependence that extends to at least the third nearest-neighbor distance. Our basis included the s and p orbitals on both Mg and B in a non-orthogonal two-center representation. A wavefunction analysis of our LAPW results shows that the bands up to the Fermi level, ε_F, are strongly dominated by the B p states with very little contribution from the Mg ions. It turns out, however, that an accurate TB fit including only the B orbitals is impossible, and therefore the Mg s and p orbitals were included in the fit. Furthermore, to obtain a highly accurate fit it was essential to block diagonalize the Hamiltonian at the high symmetry points Γ, A, L, K and H. We find that at a given set of lattice parameters (c,a) we can perfectly reproduce the energy bands of MgB_2. A comparison is shown in Fig. 1, where the solid and broken lines represent the LAPW and TB bands, respectively, at the LDA values of the equilibrium lattice parameters. The TB bands are in excellent agreement with the LAPW bands, including the two-dimensional B-σ band in the $\Gamma \rightarrow A$ direction just above ε_F, which has been identified as hole band controlling superconductivity.[5,7] The RMS fitting error is 2 mRy for the total energy, and close to 10 mRy for the first five bands. Beyond the fifth band our fit is not as accurate, as the Mg *d*-bands, which are not included in our Hamiltonian, come into play. The values of our TB parameters are given in Table I following the notation of Bernstein *et al.*[15] In this table we also show, for the convenience of the reader, the actual Slater-Koster pa-

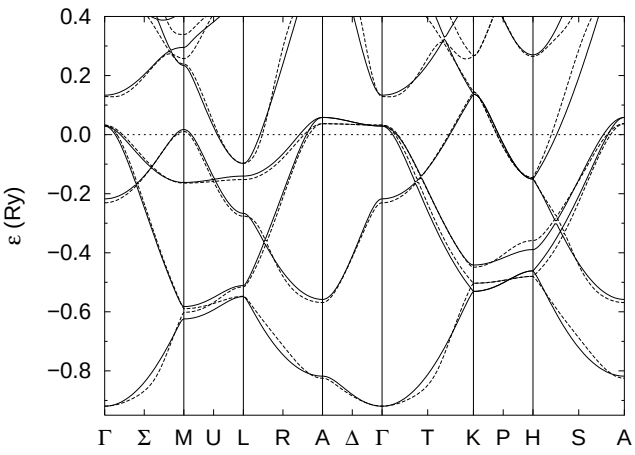

FIG. 1. The band structure of MgB_2 in the AlB_2 structure at the theoretical equilibrium volume, as determined by the full-potential LAPW method (solid lines) and our tight-binding parametrization (dashed lines). The Fermi level is at $\varepsilon = 0$.

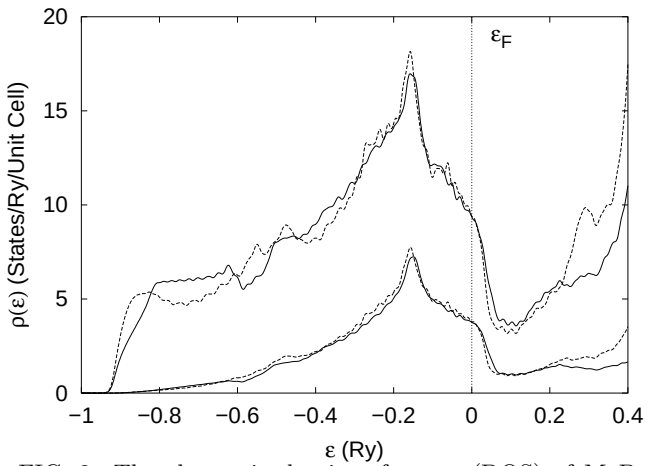

FIG. 2. The electronic density of states (DOS) of MgB_2 in the AlB_2 structure at the theoretical equilibrium volume, comparing the total DOS as determined by the full-potential LAPW method (upper solid line) and our tight-binding parametrization (upper dashed line), and the partial single-atom B-p decomposition (lower lines). The LAPW result decomposition was determined inside the muffin-tin and then scaled by a factor of 2.37 (see text).

rameters for three or four nearest neighbors determined from our formulas for the specific LDA equilibrium values of the lattice constants.

In Fig. 2 we show a comparison of TB and LAPW densities of states. There is an excellent agreement in both the total DOS and the B p-like DOS. To facilitate the comparison we have normalized the muffin-tin decomposed LAPW values so that the contributions from the angular momentum components add up to the total DOS, as is the case in the TB. For the Boron states this amounted to multiplying the decomposed values by 2.37. The B s-components of the DOS have their strongest presence at the bottom of the valence band, from -0.8 Ry to -0.6 Ry on our scale. They are much smaller than the p-like DOS, so we chose not to include them in Fig. 2. Additionally, we have omitted the Mg p-like DOS, which is also small below ε_F, although it becomes significant above ε_F. Our TB value of the total DOS at ε_F is $N(\varepsilon_F) = 0.69$ states/eV, which is almost identical to that found from our direct LAPW calculation. This value of $N(\varepsilon_F)$ corresponds to the LDA equilibrium volume and is slightly smaller than the value of 0.71 states/eV reported by other workers[4–8] at the experimental volume. Using our value of $N(\varepsilon_F)$ and the measured value[3] of the specific heat coefficient γ we infer a value of $\lambda = 0.65$ which is consistent with the high superconducting transition temperature in MgB_2. It should also be noted that the B-p states contribute 81% of the DOS at ε_F.

Our TB-Hamiltonian also provides an accurate description of the energetics of MgB_2, which is expected to be very useful for other theoretical studies. We have further tested our parameters by computing the TB equilibrium structure. We find an equilibrium of c = 6.66 a.u. and a = 5.79 a.u., in good agreement with the LAPW result. At c/a = 1.14 (the experimental value), we deduce a bulk modulus of B = 165 GPa which in good agreement with the experimental value of 120GPa and with the calculated value of 147 GPa reported by Bohnen *et al.*[6]

The TB parameters presented in this paper give a very accurate description of the band structure of MgB_2. The availability of this Hamiltonian should motivate the calculation of other properties of this important material.

We thank I. I. Mazin and D. J. Singh for useful discussions. This work was supported by the U. S. Office of Naval Research. The development of the tight-binding codes was supported in part by the U. S. Department of Defense Common HPC Software Support Initiative (CHSSI).

[1] J. Nagamatsu *et al.*, Nature **410**, 63 (2001).
[2] P. C. Canfield *et al.*, Phys. Rev. Lett. **86**, 2423 (2001).
[3] Y. Wang, T. Plackowski, and A. Junod, Physica C **355**, 179 (2001).
[4] J. M. An and W. E. Pickett, Phys. Rev. Lett. **86**, 4366 (2001).
[5] J. Kortus *et al.*, Phys. Rev. Lett. **86**, 4656 (2001).
[6] K.-P. Bohnen, R. Heid, and B. Renker, Phys. Rev. Lett. **86**, 5771 (2001).
[7] Y. Kong, O. V. Dolgov, O. Jepsen, and O. K. Andersen, Phys. Rev. B **64**, 020501 (2001).
[8] A. Y. Liu, I. I. Mazin, and J. Kortus, condmat/0103570 (2001).
[9] M. Mehl, D. Papaconstantopoulos, and D. Singh, condmat/0104548 (2001).
[10] R. E. Cohen, M. J. Mehl, and D. A. Papaconstantopoulos, Phys. Rev. B **50**, 14694 (1994).
[11] M. J. Mehl and D. A. Papaconstantopoulos, Phys. Rev. B **54**, 4519 (1996).
[12] O. K. Andersen, Phys. Rev. B **12**, 3060 (1975).
[13] D. Singh, H. Krakauer, and C. S. Wang, Phys. Rev. B **34**, 8391 (1986).
[14] L. Hedin and B. L. Lundqvist, Journal of Physics C **4**, 2064 (1971).
[15] N. Bernstein *et al.*, Phys. Rev. B **62**, 4477 (2000).

TABLE I. Tight-binding parameters for MgB_2, generated following the methods of Mehl and Papaconstantopoulos[11] and Bernstein *et al.*[15]. Also shown are the generated Slater-Koster tight-binding parameters for the nearest neighbors at the LDA equilibrium lattice constants, a = 5.75 a.u. and c = 6.53 a.u. On-site energies are generated from the "densities" of like atoms, that is, the Mg on-site parameters come from the density of Mg atoms, and the B on-site parameters from the density of B atoms. $F(R)$ is the cutoff function from equation (2) of Berstein *et al.*[15], with R_c = 12.5 a.u. and L_c = 0.5a.u. All energies are in Rydbergs, all distances in a.u.

Mg-Mg Interactions								
On-site Parameters ($\lambda = 0.93961\ a.u.^{-1/2}$)								
ℓ	α_ℓ	β_ℓ	γ_ℓ	χ_ℓ	LDA Equilibrium Values			
s	0.02169	-0.25368	-0.04017	19.84215	0.03516			
p	0.39868	-0.22303	1.35834	53.36624	0.52322			
Hopping Terms: $H_{\ell\ell'\mu}(R) = (a_{\ell\ell'\mu} + b_{\ell\ell'\mu}R + c_{\ell\ell'\mu}R^2)\exp(-g^2_{\ell\ell'\mu}R)F(R)$								
$H_{\ell\ell'\mu}$	$a_{\ell\ell'\mu}$	$b_{\ell\ell'\mu}$	$c_{\ell\ell'\mu}$	$g_{\ell\ell'\mu}$	a	c	$\sqrt{3}a$	
$H(ss\sigma)$	5715.097	-310.8836	-182.0526	1.35579	-0.05372	-0.02495	-0.00009	
$H(sp\sigma)$	5704288.	541286.7	-387450.5	1.84506	-0.01259	-0.00161	-0.00000	
$H(pp\sigma)$	-1920.935	498.3775	-22.58129	1.12482	0.13720	0.09557	0.00141	
$H(pp\pi)$	2000.513	-739.8181	70.26517	1.13170	0.04414	0.03861	0.00241	
Overlap Terms: $S_{\ell\ell'\mu}(R) = (\delta_{\ell\ell'} + t_{\ell\ell'\mu}R + q_{\ell\ell'\mu}R^2 + r_{\ell\ell'\mu}R^3)\exp(-u^2_{\ell\ell'\mu}R)F(R)$								
$S_{\ell\ell'\mu}$	$t_{\ell\ell'\mu}$	$q_{\ell\ell'\mu}$	$r_{\ell\ell'\mu}$	$u_{\ell\ell'\mu}$	a	c	$\sqrt{3}a$	
$S(ss\sigma)$	1.04886	-1.27181	0.55382	1.01629	0.18512	0.12683	0.00767	
$S(sp\sigma)$	0.41781	0.03630	-0.00873	0.63396	0.19274	0.13373	-0.00815	
$S(pp\sigma)$	-24.36368	0.17541	0.41661	1.07340	-0.07174	-0.01867	0.00101	
$S(pp\pi)$	-68.95974	5.97517	2.55826	1.19338	0.08007	0.04731	0.00088	
B-B Interactions								
On-site Parameters ($\lambda = 0.79205\ a.u.^{-1/2}$)								
ℓ	α_ℓ	β_ℓ	γ_ℓ	χ_ℓ	LDA Equilibrium Values			
s	-0.16521	-0.00022	0.02579	0.09088	-0.09356			
p	0.38802	0.00060	0.00566	0.01918	0.40383			
Hopping Terms: $H_{\ell\ell'\mu}(R) = (a_{\ell\ell'\mu} + b_{\ell\ell'\mu}R + c_{\ell\ell'\mu}R^2)\exp(-g^2_{\ell\ell'\mu}R)F(R)$								
$H_{\ell\ell'\mu}$	$a_{\ell\ell'\mu}$	$b_{\ell\ell'\mu}$	$c_{\ell\ell'\mu}$	$g_{\ell\ell'\mu}$	$a/\sqrt{3}$	a	c	$2a/\sqrt{3}$
$H(ss\sigma)$	-7.31550	2.09241	-0.23379	0.85573	-0.25908	-0.04471	-0.03032	-0.02881
$H(sp\sigma)$	-146.6733	64.75572	-8.57386	1.21983	-0.18743	-0.01112	-0.00538	- 0.00484
$H(pp\sigma)$	-296.2214	128.0942	-10.42990	1.17220	0.14703	0.03537	0.01210	0.01030
$H(pp\pi)$	167.1287	-84.95581	9.40729	1.16057	-0.12834	-0.00448	0.00204	0.00232
Overlap Terms: $S_{\ell\ell'\mu}(R) = (\delta_{\ell\ell'} + t_{\ell\ell'\mu}R + q_{\ell\ell'\mu}R^2 + r_{\ell\ell'\mu}R^3)\exp(-u^2_{\ell\ell'\mu}R)F(R)$								
$S_{\ell\ell'\mu}$	$t_{\ell\ell'\mu}$	$q_{\ell\ell'\mu}$	$r_{\ell\ell'\mu}$	$u_{\ell\ell'\mu}$	$a/\sqrt{3}$	a	c	$2a/\sqrt{3}$
$S(ss\sigma)$	0.08974	-0.05865	0.00446	0.60130	0.24535	0.05320	0.03092	0.02870
$S(sp\sigma)$	14.02893	-2.43293	0.33914	1.27302	0.14823	0.00581	0.00208	0.00181
$S(pp\sigma)$	-60.70629	-0.47590	3.29498	1.32165	-0.25833	0.01141	0.00558	0.00497
$S(pp\pi)$	18.98764	6.13369	-3.44742	1.41889	0.00689	-0.00321	-0.00112	-0.00096
Mg-B Interactions								
Hopping Terms: $H_{\ell\ell'\mu}(R) = (a_{\ell\ell'\mu} + b_{\ell\ell'\mu}R + c_{\ell\ell'\mu}R^2)\exp(-g^2_{\ell\ell'\mu}R)F(R)$								
$H_{\ell\ell'\mu}$	$a_{\ell\ell'\mu}$	$b_{\ell\ell'\mu}$	$c_{\ell\ell'\mu}$	$g_{\ell\ell'\mu}$	$\sqrt{\frac{1}{3}a^2 + \frac{1}{4}c^2}$	$\sqrt{\frac{4}{3}a^2 + \frac{1}{4}c^2}$	$\sqrt{\frac{7}{3}a^2 + \frac{1}{4}c^2}$	
$H(ss\sigma)$	-15.40626	8.92332	-2.25890	1.06263	-0.11887	-0.01709	-0.00257	
$H(sp\sigma)$	-22.65145	5.35089	-0.60679	1.03205	-0.07642	-0.00612	-0.00093	
$H(pp\sigma)$	98.38228	-45.01479	6.05711	1.20823	0.02245	0.00196	0.00019	
$H(pp\pi)$	-94.47230	33.60639	-4.25418	1.21106	-0.03269	-0.00152	-0.00013	
$H(ps\sigma)$	7.80580	1.71300	-0.22442	1.03201	0.07662	0.00308	0.00015	
Overlap Terms: $S_{\ell\ell'\mu}(R) = (t_{\ell\ell'\mu} + q_{\ell\ell'\mu}R + r_{\ell\ell'\mu}R^2)\exp(-u^2_{\ell\ell'\mu}R)F(R)$								
$S_{\ell\ell'\mu}$	$t_{\ell\ell'\mu}$	$q_{\ell\ell'\mu}$	$r_{\ell\ell'\mu}$	$u_{\ell\ell'\mu}$	$\sqrt{\frac{1}{3}a^2 + \frac{1}{4}c^2}$	$\sqrt{\frac{4}{3}a^2 + \frac{1}{4}c^2}$	$\sqrt{\frac{7}{3}a^2 + \frac{1}{4}c^2}$	
$S(ss\sigma)$	1.74820	0.13546	0.07434	0.82425	0.16873	0.04450	0.01278	
$S(sp\sigma)$	15.27243	3.72217	0.27051	1.09173	0.14959	0.00848	0.00081	
$S(pp\sigma)$	-4.51769	-4.96427	0.71842	0.95339	-0.17503	-0.00229	0.00188	
$S(pp\pi)$	846.58108	265.43883	-10.03535	1.30600	0.06108	0.00187	0.00007	
$S(ps\sigma)$	-2.81156	0.20700	-0.40404	0.92459	-0.19812	-0.04168	-0.00940	